



TEST REPORT

Report No. :W2026-02954

Applicant name : HANGZHOU KETA HOME FURNISHING CO. , LTD
Applicant address : ROOM 320, BUILDING A NO. 776 JIANSHE 1ST ROAD XIAOSHAN ECONOMIC & TECHNOLOGICAL DEVELOPMENT ZONE HANGZHOU CITY, ZHEJIANG PROVINCE, CHINA
Contact person : /
Sample description : The following sample(s) was/were submitted and identified on behalf of the client as
Item name : SARA-WHITE
Colour : WHITE
Style No. : /
Order No. : /
Composition : 100% POLYESTER
Other information : /
Date received : March 16, 2026
Test completed : March 19, 2026
Remark : /
Test details : Refer to the test details requested by the applicant on next page(s).



Approved by

Date of Approval: March 19, 2026

Zhejiang ZTT Testing Co.,Ltd.

Add.: No. 18, 2nd Jingdu Rd. , Zhejiang Haining Warp Knitting Industrial Zone, Zhejiang, China.
Tel.: 86-573-87989122 Fax.: 86-573-87989121 Http: // www.zttcn.com



TEST REPORT

Report No. : W2026-02954

Test details requested by the applicant :

Test method 1 of NFPA 701:2023 Standard Methods of Fire Tests for Flame Propagation of Textiles and Films

Conditioning

Prior to testing at least 30 minutes at 105°C ±3°C

Test results

Specimen No:	Mass of specimen Before test (g)	Mass of specimen After test (g)	Mass loss (Percent)	After flame time (s)	Burning time on floor (s)
1	10.3991	8.2058	21.09	0	0
2	10.5209	9.1235	13.28	0	0
3	11.0159	8.9153	19.07	0	0
4	11.1632	9.3329	16.40	0	0
5	10.8905	8.7811	19.37	0	0
6	10.8637	8.2765	23.82	0	0
7	10.9918	9.0123	18.01	0	0
8	10.8897	8.3457	23.36	0	0
9	10.2474	8.0056	21.88	0	0
10	10.8409	8.7634	19.16	0	0
AVE	/	/	19.54	0	0

Criteria for test method 1 (Chapter 10):

1. Fragments or residues of specimens that fall to the floor of the test chamber shall not continue to burn for more than an average of 2 seconds per specimen for the sample of 10 specimen.
2. The average weight loss of the 10 specimen in a sample shall be 40 percent or less.
3. No individual specimen's percent mass loss shall deviate more than 3 standard deviations from the mean for the 10 specimens.
4. When a retest is required, no individual specimen's percent mass loss in the second set of specimens shall deviate from the mean value by more than 3 standard deviations calculated for the second set.

Zhejiang ZTT Testing Co.,Ltd.

Add.: No. 18, 2nd Jingdu Rd., Zhejiang Haining Warp Knitting Industrial Zone, Zhejiang, China.
Tel.: 86-573-87989122 Fax.: 86-573-87989121 Http:// www.zttcn.com






TEST REPORT

Report No. : W2026-02954

5. When a sample does not demonstrate passing performance in accordance with all of the conditions indicated above, the material shall be recorded as having failed Test Method 1.

Conclusion: The tested sample as received meets the requirements of Test Method 1 of NFPA 701:2023.

Remark: This item is only approved by CNAS.

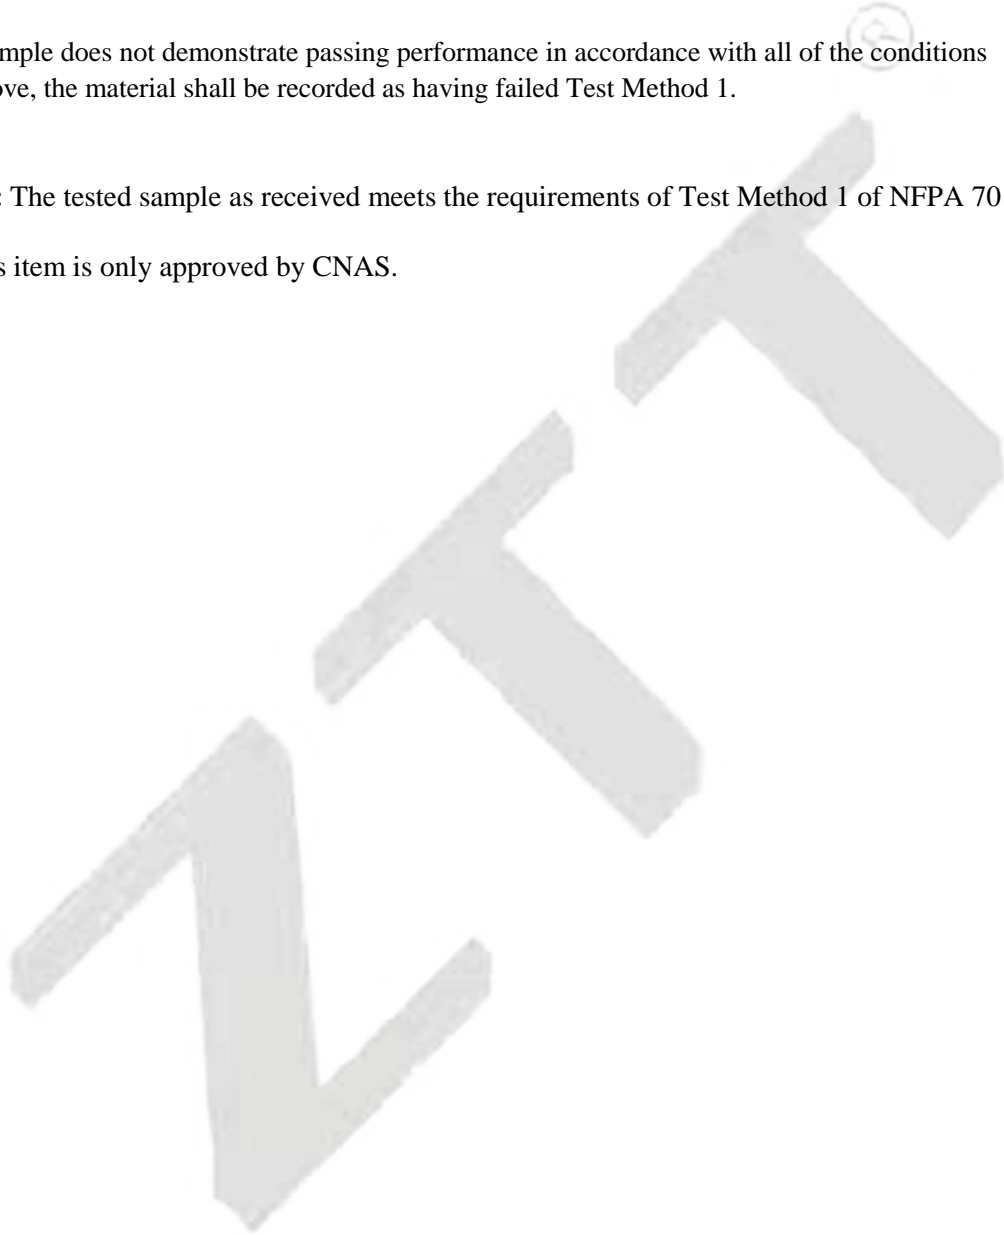

Zhejiang ZTT Testing Co.,Ltd.

Add.: No. 18, 2nd Jingdu Rd., Zhejiang Haining Warp Knitting Industrial Zone, Zhejiang, China.
Tel.: 86-573-87989122 Fax.: 86-573-87989121 Http: // www.zttcn.com



TEST REPORT

Report No.: W2026-02954

Sample Photo



***** End of Report *****



Zhejiang ZTT Testing Co.,Ltd.

Add.: No. 18, 2nd Jingdu Rd., Zhejiang Haining Warp Knitting Industrial Zone, Zhejiang, China.
Tel.: 86-573-87989122 Fax.: 86-573-87989121 Http: // www.zttcn.com